



Technical Sciences
Academy of Romania
www.jesi.astr.ro

Journal of Engineering Sciences and Innovation

Volume 2, Issue 4 / 2017, pp. 59-69
<http://doi.org/10.56958/jesi.2017.2.4.59>

*D. Chemical Engineering, Materials Science and
Engineering, Natural Resources*

Received 18 September 2017

Accepted 6 December 2017

Received in revised form 3 November 2017

The effects of change the energy conditions and synthesis media activity on nickel aluminides type and proportion

COJOCARU MIHAI*, DRUGĂ LEONTIN, TUDOSE FLORICĂ

*University POLITEHNICA of Bucharest, 313 Splaiul Independentei, Sector 6, 060042
Bucharest, Romania*

Abstract. The work summarizes aspects related to the effects of change the energy conditions of the synthesis of nickel aluminides by mechanical alloying in balls mills, namely of the activity of powdery media used for alitiation of nickel matrixes. The experimental research revealed that the type and proportion of nickel aluminides can be changed in a controllable manner by rigorous selection of the type of mill used and of its operating conditions. The alitiation has been made in powdery media including pure aluminium powder or mixtures of aluminium and iron powder (in equal weight percentages) as aluminium suppliers, instead of ferro-aluminium powders which are currently used. The alitiation resulted in layers with complex phase's compositions which are directly dependent on processing temperature, matrix composition and alitiation media composition. It was demonstrated that the Al-Fe mixture of powders represents a viable alternative for the ferro-aluminium powder for the alitiation process.

Keywords: nickel aluminides, mechanical alloying in balls mills, alitiation in powdery solid media, nickel based super-alloys.

1. Introduction

The nickel aluminides show a particular interest for development, by means of different techniques, of protective layers against high temperature oxidation of nickel/nickel alloys components which support high mechanical - thermal loads in rich oxygen potential environments.

Among the five aluminides of the Al-Ni system (Al_3Ni_2 , Al_3Ni_5 , Al_3Ni , $AlNi_3$, $AlNi$) [1], the latest two are characterized by a particular thermodynamic stability

*Correspondence address: cojocarumihaiovidiu@yahoo.co.uk

at temperatures over 1000°C along with ductility, hardness, mechanical resistance and resistance against oxidation, carburizing and nitriding [2].

The development of protective layers is recommended when the change of chemical composition of metallic matrixes by elements contributing to the increase of their oxidation resistance results implicitly in the alteration of the mechanical characteristics of them [3].

The methods for synthesis of nickel aluminides are various [3, 4], a first classification exhibiting a first group which includes the processing methods from melting of elements, namely a second group which refers to the processing methods from powders of the elemental components [3]; in this last group the mechanical alloying [3, 5] and the alitiation [6, 7, 8, 9] own a significant place.

The choose of the method for development the protective layers, in situ or by depositing of nickel aluminides is based on the necessity to ensure their perfect adherence to the support. Another important issue considered is the limiting of the occurrence of porosity: the notable differences between the diffusion coefficients of aluminium in nickel namely nickel in aluminium, corroborated with the differences between the mass fluxes transferred by diffusion from/to the alitiation medium, represent the main factors generating porosity [10, 11].

Therefore, it is necessary to select and control carefully the specific parameters for synthesis and processing in order to achieve the phases composition required in the protective layer in accordance with the exploiting demands of the component targeted.

2. Materials and Equipment used in the research

The aluminium (purity 99,2%) and nickel powders (purity 99,9%) obtained by air pulverization, namely by Sherrit hydro-metallurgical process have been used in research in order to identify the effects of change the energy conditions of the nickel aluminides synthesis by **mechanical alloying in balls mills**.

The particle mean diameters of the two powders were 12,5µm, for aluminium and 90µm for nickel; in the mixtures processed in the balls mills, these components have been used in equal weight percentages.

Two types of ball mills have been used, one ceramic mill of 1,5 l which uses ceramic milling bodies with a total weight of 0,3 kg and one refractory steel mill of 2,5 l which uses milling bodies from hard alloys of sintered Widia carbides with a total weight of 4,5 kg.

The similarities in the operation of the two ball mills are related to their turning speed - 102rot/min (about. 85% of its critical turning speed), but the differences are linked to the value of rapport between the weight of the milling bodies (M_{cm}) and the weight of the powder mixture (M_{ap}) which is to be processed: $M_{cm}/M_{ap} \sim 110$ for the refractory steel mill namely $M_{cm}/M_{ap} < 10$ for the ceramic mill.

The processing has been performed at $T_{ambient}$ (initial temperature) in air, for different periods of time in the range 5 ... 50h.

The alitiation of the nickel matrixes (electrolytic nickel with purity of 99,2%, namely nickel based superalloys -INCONEL 718 with composition in the limits of W 2.4668 grade) was achieved in powdery mixtures including Al-Al₂O₃-NH₄Cl, namely powders mixtures (Al+Fe) in equal weight percentages in the presence of NH₄Cl in amount of 2%.

These powders have been used instead of ferro-aluminium which is currently found in the industrial practice; it was introduced subsequently in the alitiation receipts in order to limit the tendency of adhesion of the mixture components to the surface of metallic products processed.

The thermochemical processing has been realized at temperatures below and above the aluminium melting temperature (640°...1000°C), in electric furnaces with automatic control of the thermal regime.

The samples have been packed in solid powdery mixtures (as suppliers of active aluminium) inside sealed metallic boxes and hold for the processing time.

The capacity of powdery mixture which included aluminium powder with 26% rich aluminium nickel aluminides (AlNi, Al₄Ni₃, Al₃Ni₂) to provide itself, or in the presence of Al₂O₃ and NH₄Cl (1%), a proper alitiation process of the nickel matrixes has been investigated.

The X-Ray diffraction by means of X'pert PRO MPD PANalytical and DRON 3 type diffractometers and the electronic microscopy by means of Quanta Inspect F50 microscope have been used for investigation of the results.

3. Results of the Experimental Researches. Interpretations

The calculation of the total energy (Et) released by the milling balls (in the two mills) during processing the Al-Ni powder mixtures by mechanical alloying in balls mills has considered the geometrical and operational characteristics of the mills, the milling bodies weight, the material (powder mixture) weight the mills loading and other [12, 13, 14, 15, 16, 17, 18].

The results of the calculation of the kinetic and potential energy of the ceramic milling bodies in ceramic mill revealed that for the given experimental conditions, the maximum energy released by the milling bodies was <1J/rot (0,6J/rot). By contrast, the energy released by the hard alloys milling bodies in the refractory steel mill was about one order higher, namely ~7J/rot.

In these energy conditions, the degree of transformation of Al-Ni powder mixture in nickel aluminides is obvious different: max 5% is reached for the low energy ceramic mills but 25% is attained in the high energy mills; consequently, the type of synthesized aluminides (Fig.1) changes also significantly due to the change of the mechanisms for their generation.

In the low energy mills will develop nickel rich aluminides of type Al₃Ni₅, the synthesis being initiated by the germination of the solid solution of aluminium in nickel; during processing time, according to the principle of sequence of transformations, the saturation of the solid solution with aluminium continues and

consequently the Al_3Ni_5 will develop once with reaching the minimum concentrations for their germination.

Rich aluminium aluminides (Fig.1) will develop preponderantly in the case of high energy ball mills, the explanation being related to the extremely high value of the nickel diffusion coefficient of nickel in aluminium, which is different with orders of magnitude against that of aluminium in nickel [19, 20, 21].

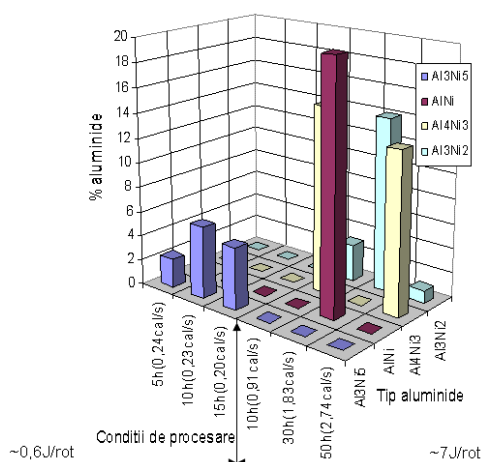


Fig. 1. Histogram showing the dependency between proportion and type of nickel aluminides and the energy of balls mills used for mechanical alloying.

In these conditions will probably occur the initiation of a process of auto-synthesis of which premises have been created by the significant increase of the local temperature (at the level of the contacts between particles); this temperature increase is due to the transformation of some mechanical energy in thermal energy together with the implications related to this phenomenon.

In the case of mechanical alloying, the increase of the defects concentrations will result in the increase of the nickel solubility in aluminium from 0% (in normal conditions) up to ~10% [3].

By change the mechanical alloying conditions such as the energy released by the milling balls to be controlled rigorously, also the proportion of the nickel aluminides in the mixtures of powders aluminium-nickel can be controlled; the nature of aluminides is also monitored depending on requirements such as to develop either rich nickel aluminides or rich aluminium aluminides.

The researches in the field of aluminides synthesis by alitation in powdery mixtures of the nickel matrixes have revealed the fact that the activity of the media composed of mixtures of powders of iron and aluminium in equal weight percentages is considerable lower than that of the media which contain aluminium powder.

The use of the mixtures of powders of iron and aluminium instead of ferro-aluminium powder is based on the hypothesis that by thermodynamic point of view, the development of Al-Fe intermetallic compounds (AlFe , Al_5Fe_2 , Al_3Fe identified by Xray diffraction-Fig.3) can occur very probable also during heating of the powdery mixtures which contain these elements in pure state [22] - (Fig.2).

This conclusion was confirmed by Xray diffraction of a sample from the iron and aluminium mixture powders (in equal weight percentages) which was thermally processed for 3 hours at 950°C (Fig.3).

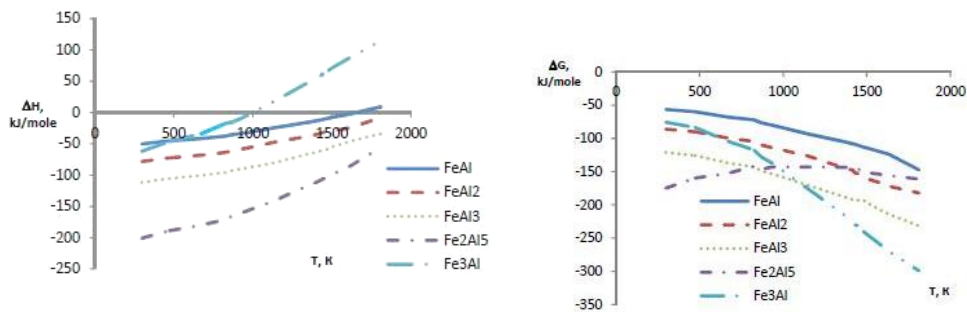


Fig. 2. Change of the enthalpy and free Gibbs energy with temperature during synthesis of the intermetallic compounds in the Al-Fe system [acc. 22].

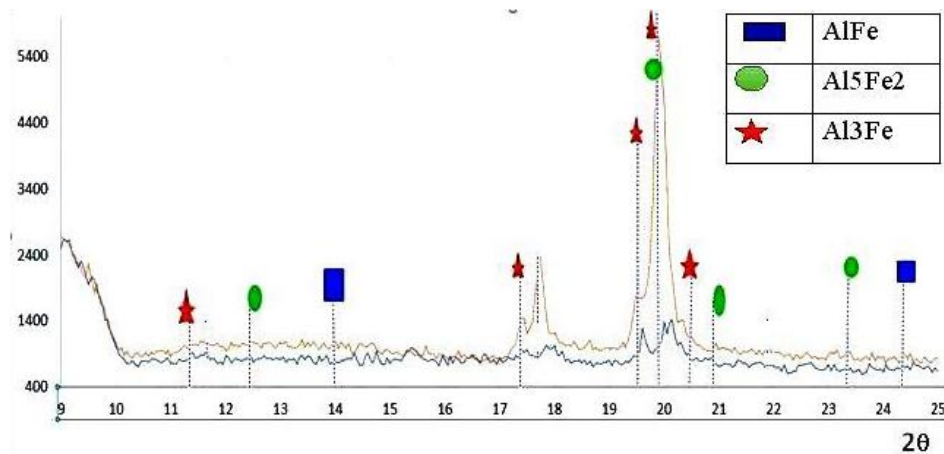


Fig. 3. The diffractograms of the ferro-aluminium powders (superior) and of the mixture of aluminium and iron powders, in equal mass proportions, thermally processed at $950^\circ\text{C}/3\text{h}$.

In these conditions it was estimated that there are no major differences between the alitiation capacity of the powdery mixtures which contain ferro-aluminium powder and that of the mixtures of iron and aluminium powders.

This is due to the fact that the general kinetics of the process are mainly determined by the kinetics of reactions of development and decomposition of the aluminium chlorides at the level of the catalytic metallic surfaces or by the transfer through diffusion of the aluminium from the combinations where this is available in the alitiation medium.

Note: In the industrial practice, the powder of ferro-aluminium is used on large scale for the realization of the mixtures used for alitiation both by practical and economic considerations. By practical, the homogenization of the mixtures of aluminium and iron powders is difficult due to the differences between the densities of the two metals, and economical, the iron and aluminium powders have higher prices than the ferro-aluminium powder.

The results of the experimental researches confirmed the initial assumptions (Fig.4÷8), indicating major differences both in the growth kinetics of alitiation layers (Fig.8) and also in their chemical and phases compositions depending on processing conditions (mainly, the alitiation medium composition).

The different activities of the media used for alitiation in powdery media, governed by the presence of aluminium or Al-Fe compounds, influenced the chemical and phases composition of the alitiation layers obtained on the Inconel 718 matrixes (Fig.4÷7 with related tables).

The differences between the activities of the media including aluminium powder by comparison with those of the media including Al-Fe refractory products are connected to the very high thermodynamic stability of the latest (except of the Fe_3Al compound which decomposes at 555°C , the other Fe-Al intermetallic compounds are stable up to temperatures over 1150°C [23]); the transfer of aluminium in the surface of matrix subject to alitiation being realized preponderantly by diffusion through these compounds.

The analysis of distribution of the aluminium in the alitiation layers in different conditions (composition of the powdery medium/temperature/time of isothermal holding) confirms that sometimes, independently on temperature, the media which contain Al-Fe intermetallic compounds are characterized by a much lower activity compared to that of those media containing aluminium.


Therefore, the flux of nickel atoms transferred by diffusion from the metallic matrix occurs mainly, such as in the superficial layer zones will be generated aluminides with a moderate content of aluminium and with relatively rich nickel content (Fig.6÷7).

When the medium is characterized by a high activity, the flux of aluminium atoms from the medium is leading such as in the zones adjacent to the surface will be generated aluminides with some rich aluminium concentrations (Fig.4÷5).

Independently of situation, the alitiation layer is characterized by the specific phases sequence which states its exploitation behaviour: the layer with a rich aluminium


content has a high brittleness and needs an additional annealing to the alitiation in order to redistribute the aluminium by diffusion and to decrease its concentrations compared to the layers with a moderate content of aluminium and nickel which have a proper exploitation behaviour.

The EDS analysis of chemical composition related to the different zones of the alitiation layer revealed that this it is composed of a sequence of nickel aluminides, either simple or alloyed, rich in aluminium or nickel, depending on the rapport between the medium activity and that of the nickel from matrix, sigma phases and very probable carbides of type $M_{23}C_6$ and/or MC in the case of superalloy INCONEL 718.

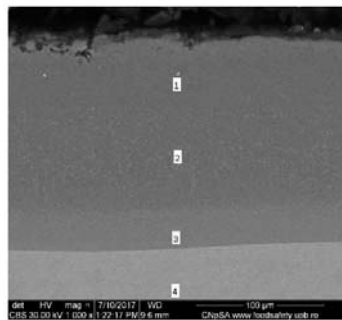


Zone	%Al	%Ti	%Cr	%Fe	%Ni	%Nb
1	63,22	0,03	8,11	8	18,21	2,43
2	63,37	0,02	8,08	-	25,42	3,1
3	34,72	0,75	10,84	12,07	32,06	9,56
4	0,38	1,14	18,67	20,15	50,5	9,17

Fig. 4* The microstructure of the aluminides layer developed by alitiation of the Inconel718 matrix in a powdery mixture (50%Al+49%Al₂O₃+1%NH₄Cl) at 900°C/5h); the above table shows the chemical composition (in wt%) of the marked zones.

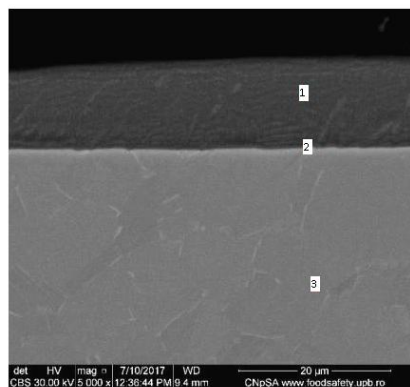


Zone	%Al	%Ti	%Cr	%Fe	%Ni	%Nb
1	55,88	0,08	8,06	8,5	24,55	2,93
2	1,02	1,18	18,82	19,3	49,03	10,65
3	-	1,14	18,24	18,73	49,09	12,79

Fig.5 The microstructure of the aluminides layer developed by alitiation of the Inconel718 matrix in a in a powdery mixture (50%Al+49%Al₂O₃+1%NH₄Cl) at 640°C/2h); the above table shows the chemical composition (in wt%) of the marked zones.

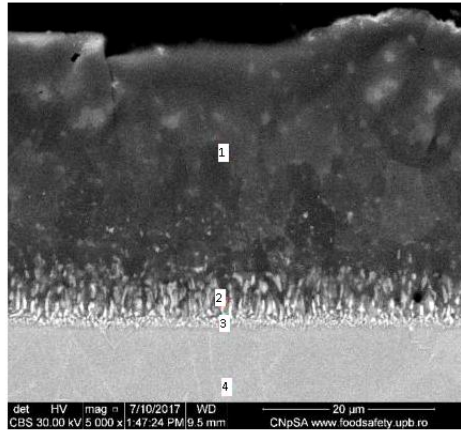

Zona	%Al	%Ti	%Cr	%Fe	%Ni	%Nb
1	36,61	0,03	6,58	13,76	36,2	6,82
2	18,68	1,2	19,75	12,28	32,96	15,13
3	4,52	1,95	27,78	23,9	23,46	18,38
4	0,26	1,36	18,08	19	48,75	12,54

Fig. 6 The microstructure of the aluminides layer developed by alitiation of the Inconel718 matrix in a powdery mixture (49%Al+49%Fe+2%NH₄Cl) at 900°C/5h); the above table shows the chemical composition (in wt%) of the marked zones.

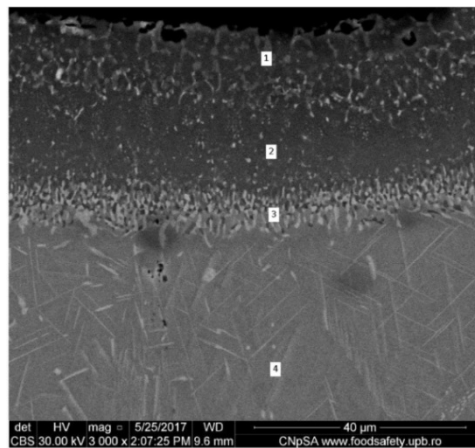


Zona	%Al	%Ti	%Cr	%Fe	%Ni	%Nb	%M o
1	25,27		11,9	23,61	38,83		
2	23,62		5,6	8,26	62,02		
3	3,94	1,06	29,63	22,14	22,81	14,64	5,61
4		1,07	17,57	18,18	44,3	9,62	9,18

Fig.7 The microstructure of the aluminides layer developed by alitiation of the Inconel718 matrix in a powdery mixture (49%Al+49%Fe+2%NH₄Cl) at 300°C/1h + 650°C/3h +950°C/20h), the above table shows the chemical composition (in wt%) of the marked zones.

The different activities of the two types of solid powdery media used for alitiation led to different saturation kinetics and distinct chemical and phases compositions. With regard to the media including aluminium powder, the superficial zones of the layer reach high aluminium concentrations (56%..63% weight) depending on the rapport between aluminium alitiation temperature and melting temperature and the layer depths vary in the limits 13µm (640°C/20h) and 162µm (900°C/5h) - Fig.8.

The dimensions of the alitiation layers achieved in the case of use of the powder of iron and aluminium are significantly lower than those obtained through alitiation in similar conditions (processing time/temperature) in media including aluminium powder; they vary little for consistent isothermal holding times 32,5µm/900°C/5h→ 33µm/300°C/1h +650°C/3h +950°C/20h - (Fig.8).

The particular thermodynamic stability of the nickel aluminides demonstrated that the use of the mixtures of aluminium powder and nickel aluminides as active components of the alitiation powdery media do not represent a very interesting solution (regimes 5 and 6 from Fig.8); the activity of these media is slightly higher than that of the media including refractory compounds of iron and aluminium mainly due to the aluminium which is free in the composition of these mixtures.

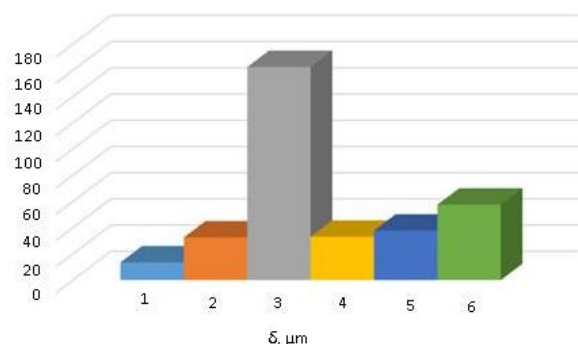

Alitiation regimes:

- 1-640°C/20h in powders mixtures 50%Al+49%Al₂O₃+1%NH₄Cl - **INCONEL 718**
- 2-900°C/5h in powders mixtures 49%Al+49%Fe+2%NH₄Cl - **INCONEL 718**
- 3-900°C/5h in powders mixtures 50%Al-49%Al₂O₃-1%NH₄Cl - **INCONEL 718**
- 4-300°C/1h+650°C/3h+950°C/20h in mixtures 49%Al+49%Fe+2%NH₄Cl - **INCONEL 718**
- 5-1000°C/30h in powders mixtures 50%(Al+26%AlNi aluminides)+49%Al₂O₃+1%NH₄Cl - **Ni**
- 6-1000°C/30h in powders mixtures 100% (Al+26%AlNi aluminides) - **Ni**

Fig. 8. Nomograph showing the different growth kinetics of the alitiation layers developed on INCONEL 718, namely pure nickel, in different processing conditions.

4. Conclusions

1. With regard to the *mechanical alloying in balls mills*:

- the low values of the rapport between the weight of the milling bodies and the weight of the material subject to the mechanical alloying, which is an expression of the low kinetic energy of the milling bodies and also the low free height for drop of the milling bodies, which is an expression of the low potential energy of the milling bodies, certifies that nickel aluminides with rich nickel content (Al_3Ni_5) will be preponderantly obtained; the energies released by the milling bodies in these circumstances are below 1J/rot;

- the high values of the $M_{\text{cm}}/M_{\text{ap}}$ rapport together with high free heights for dropping of the milling bodies, certify that rich aluminium aluminides (AlNi , Al_4Ni_3 , Al_3Ni_2) will mainly develop; the energies released by the milling bodies in these conditions are over 7J/rot; the holding time chosen for the mechanical alloying influences slightly the rate of conversion of the powders mixtures in intermetallic compounds which is max. 5% for mechanical alloying in low energy balls mills (processing time~ max. 15 h), namely max 26% for high energy mills (processing times up to 50 h).

2. With regard to the *alitation in powdery media*, the experimental researches, revealed that:

- an increase of the conversion rate can be ensured by an increase of the geometrical characteristics of the balls mills;

- the mixtures of Al-Fe powders represent a viable alternative to the media which have as active component the ferro-aluminium;

- the mixtures of Al-Fe powders have a similar behaviour to that of the ferro-aluminium powder during heating and holding for alitation; the synthesis of the Al-Fe compounds (pre-available in the ferro-aluminium powder) takes place during heating and continues also during isothermal holding, such as the saturation in aluminium of the surfaces can be realized according to same mechanism;

- the media including aluminium powder are more active by comparison with those including mixtures of iron and aluminium in equal weight percentages; the lower content of aluminium in the layer alited in powdery mixtures of iron and aluminium, makes their brittleness to be much lower by comparison with that of the layers alited and developed in mixture of powders which have as active component the aluminium powder; consequently it is not necessary to apply an annealing subsequent to alitation with a view to control the content of aluminium in layer;

- both the chemical composition and also the phase composition of the alitation layer are extremely sensitive to the variation of the component nature which supplies aluminium from the powdery media used for alitation.

References

- [1] T.B. Massalski, J.L. Murray, K.H. Bennet and H. Baker, *Phases Diagrams*, American Society for Metals, Metals Park OH, USA, 1986.

- [2] R.W. Guard and A.M. Turkalo, *Mechanical Properties of Intermetallic Compounds* edited by J.H. Westbrook, in John Wiley & Sons Inc. p.141-160-Fractographic Studies in NiAl and Ni₃Al-by, USA, 1960.
- [3] Suryanarayana C., *Mechanical alloying and milling*, in Progress in Materials Science, vol. 46, no.1-2, 2001.
- [4] M. Cojocaru, F. Tudose, *The obtaining of the intermetallic compounds of Ni-Al system by self-propagating temperature synthesis and thermal explosion*, in Advanced Materials Research, ISSN 1662-8985, vol.114, p.132-145, July 2015, Trans Tech Publication, Switzerland.
- [5] Popescu G., and Cârceanu I., *Alierea mecanică-principii-mecanisme-aplicații*, Ed. Printech, 2007, București, Romania.
- [6] A.M. Hodge and D.C. Dunand, *Synthesis of nickel-aluminide foams by pack-aluminization of nickel foams*, Intermetallics, 9, 2001, p.581-598.
- [7] V.A. Ravi, *Pack Cementation Coatings Corrosion: Fundamentals, Testing and Protection*, vol 13A, ASM Handbook, ASM International, 2003, p. 763-771.
- [8] Ching-Yuan Bai, Yi-Jun Luo and Chun-Hao Koo, *Improvement of high temperature oxidation and corrosion resistance of superalloy IN-738LC by pack cementation*, in Surface and Coatings Technology 183, 2004, p.74-78.
- [9] Suguru Shiomi, Masao Miyake, Tetsuji Hirato and Akihiro Sato, *Aluminide Coatings Fabricated on Nickel by Aluminium Electrodeposition from DMSO₂-Based Electrolyte and Subsequent Annealing* in Materials Transactions, vol 52, nr.6, 2011, p.1216-1221
- [10] V. Rohr, *Developpment de revetements pour les aciers dechangeurs thermiques et amelioration de leur resistance a la corosionen environnement simulant les fumees de combustion de charbon*. Thèse présentée pour obtenir le titre de docteur de l'Institute National Polytechnique de Toulouse, 21 oct.2005.
- [11] K. Garbala and A. Patejuk, *Defects of Al-Ni joints caused by Kirkendall-Frenkel effect*, in Archives of Foundry Engineering, vol.10, Issue Special 1/2010, p.455-458.
- [12] Yan Bai, Fang He, Bingyan Fu and Xing Han, *Energy Calculation model of Ball Kinematics based on Ball Mill Coal Load* in International Journal of Innovative Computing, Information and Control, vol 10, nr. 5, oct. 2014, p.1715-1725.
- [13] Pritikin B.P., "Mehaniceskoe oborudovanie zavodovtvetnoi metallurghii-v.1 *Mehaniceskoe oborudovanie dleapodgotovkiših materialov* Moskva, Metallurghia, 1988, p. 231-232.
- [14] V.S. Bogdanov, S.I. Antsiferov, N.E. Bogdanov, *The Power Consumption Calculation of a Ball Drum Mill* Middle –Est of Scientific Research 18(10), 2013, p.1448-1454.
- [15] Magdalinovic N., *Calculation of energy required for grinding in a ball mill* in International Journal of Mineral Processing, vol.25, Issue 1-2, jan.1989, p. 41-46.
- [16] A.S. Andreev, V. A. Petrov, V.V. Zverevici, *Droblenie, izmelceniei grohocenie polezni hiscopaemih Ucebnicdleavuzov-M. Nedra*, 1980.
- [17] Thomas A, Fillipov L.O, *Fractures, fractals and breakage energy of mineral particles* in International Journal of Mineral Processing, vol.57, no.4, oct. 1999, p. 285-301.
- [18] M. Cojocaru, F. Tudose *Synthesis of nickel aluminides by mechanical alloying in ball mills*, in UPB Sci.Bull., Series B, vol 78, Iss.4, 2016.
- [19] G. Erdelyi, D.L. Beke, F.J. Kedves&I. Godeny, *Determination of Diffusion coefficient of Zn, Co and Ni in aluminium by resistometric method*, in Philosophical Magazine Part. B vol. 38 (Issue 5), 1978, 445.
- [20] Ken-ichi Hirano, R.P. Agarwala, Morris Cohen, *Diffusion of iron, nickel and cobalt in aluminium*, in Acta Metalurgica, vol.10, Issue 9, September 1962, p. 857-863.
- [21] Wu Quiong, Li Shu-Suo, Ma Yue and Gong Sheng-Kai, *First principles calculations of alloying element diffusion coefficients in Ni using the five-frequency model*, in Chin. Phys.B, vol. 21, No. 10, 2012.
- [22] A.I. Begunov, M.P. Kuzmin, *Thermodynamic stability of Intermetallic Compounds in Technical Aluminium* in Journal of Siberian University, Engineering & Technologies 2, 2014-7, 132-137.
- [23] G.V. Samsonov and I.M. Vinički, *Tugoplavkie soedinenia*, Moskva, Metallurghia, 1976.

